

Wieland-B16 SUPRALLOY®

CuSn6
C51900

Material Designation	
EN	CuSn6
UNS*	C51900

* Unified Numbering System (USA)

Chemical Composition (Reference)	
Sn	6 %
Cu	balance

Typical Applications
<ul style="list-style-type: none"> • Miniaturized connectors • Contact springs • Relais springs

Physical Properties*		
Electrical Conductivity	MS/m	9
	%IACS	16
Thermal Conductivity	W/(m·K)	75
Coefficient of Electrical Resistance**	10 ⁻³ /K	0.7
Coefficient of Thermal Expansion**	10 ⁻⁶ /K	18.5
Density	g/cm ³	8.80
Modulus of Elasticity	GPa	118
Specific Heat	J/(g·K)	0.377
Poisson's Ratio		0.34

* Reference values at room temperature


** Between 0 and 300 °C

Fabrication Properties	
Capacity for Being Cold Worked	excellent
Machinability	less suitable
Capacity for Being Electroplated	excellent
Capacity for Being Hot-Dip Tinned	excellent
Soft Soldering	excellent
Resistance Welding	good
Gas Shielded Arc Welding	good
Laser Welding	good


Corrosion Resistance
Resistant to seawater and industrial atmosphere. Largely insensitive to stress corrosion cracking.

Mechanical Properties			
Temper		R550	R670
Tensile Strength R _m	MPa	550–650	670–780
Yield Strength R _{p0.2}	MPa	≥ 500	≥ 660
Elongation A _{50mm}	%	≥ 16	≥ 7
Hardness HV (for information only)		170–230	200–260

Electrical Conductivity

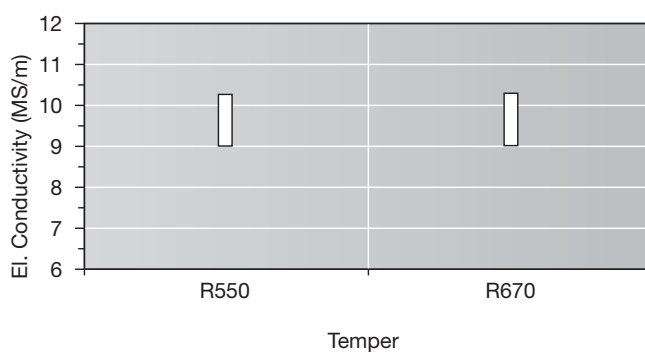


Bendability (Strip Thickness t ≤ 0.5 mm)

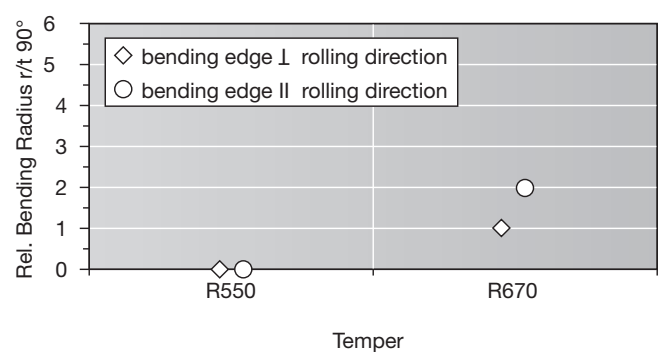

Wieland-B16 SUPRALLOY®


CuSn6
C51900

Fatigue Strength / Woehler Curve (for information only)

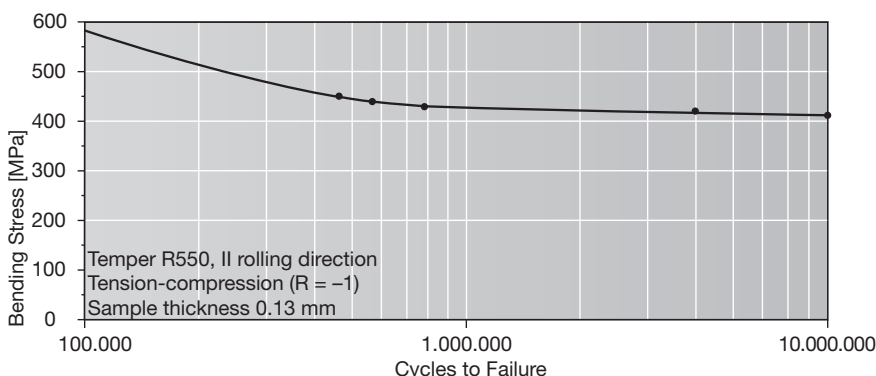

The fatigue strength is defined as the maximum bending stress amplitude which a material withstands for 10^7 load cycles under symmetrical alternate load without breaking.

Stress Relaxation (for information only)

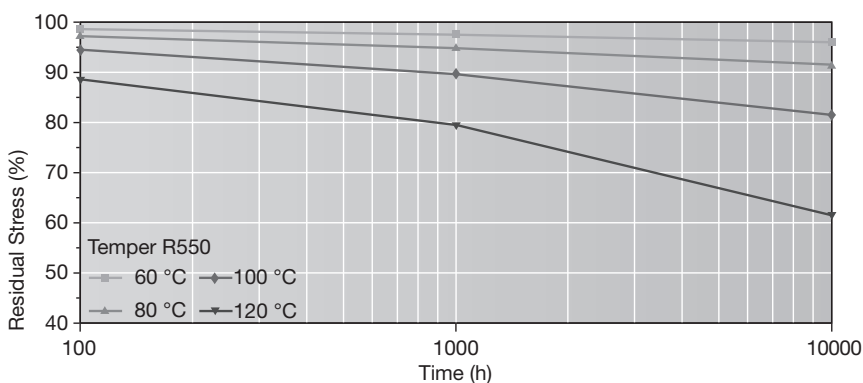

Stress remaining as a function of service temperature and time. Measured on stress relief annealed specimens parallel to rolling direction. Values extrapolated according to F. R. Larson, J. Miller, Trans ASME74 (1952) 765-775. Total stress relaxation depends on the applied stress level.

Types and Formats Available

- Standard coils with outside diameters up to 1400 mm
- Traverse-wound coils with drum weights up to 1.5 t
- Multicoil up to 5 t
- Hot-dip tinned strip
- Contour-milled strip

Dimensions Available

- Strip thickness from 0.10–0.40 mm, thinner gauges on request
- Strip width from 7 mm

Wieland-Werke AG

www.wieland.com

Rolled Products Division

Graf-Arco-Str. 36, 89079 Ulm, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-2772, info@wieland.de
Ziegeleiweg 20, 42555 Velbert-Langenberg, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-9270, info@wieland.de
Lantwattenstr. 11, 78007 Villingen-Schwenningen, Germany, Phone +49 (0)731 944-0, Fax +49 (0)731 944-7108, info@wieland.de

This leaflet is for your general information only and is not subject to revision. No claims can be derived from it unless there is evidence of intent or gross negligence. The data given are no warranty that the product is of a specified quality and they cannot replace expert advice or the customer's own tests.